

Effect of deposition temperature on the structural and surface properties of AlN by plasma enhanced atomic layer deposition

Chen Fang¹, Fang Xuan¹, Wang Shuangpeng², Niu Shouzhu¹, Fang Fang³, Fang Dan¹, Tang Jilong¹,
Wang Xiaohua¹, Liu Guojun¹, Wei Zhipeng¹

(1. State Key Laboratory of High Power Semiconductor Lasers, School of Science, and School of Photoelectric Engineering, Changchun University of Science and Technology, Changchun 130022, China; 2. National Key Laboratory of Optical and Application, Changchun Institute of Optics, Fine Mechanics and Physics, Chinese Academy of Sciences, Changchun 130022, China; 3. National Institute Silicon of LED on Si Substrate, Nanchang University, Nanchang 330047, China)

Abstract: The influence of growth temperature on the properties of aluminum nitride (AlN) films are grown by plasma enhanced atomic layer deposition (PEALD) at different deposition temperature. NH_3 and trimethylaluminum (TMA) were used as precursors, 200, 500, 800, 1 000, 1 500 cycles AlN layers were deposited at 300 °C, 350 °C and 370 °C, the growth rate, crystallinity and surface roughness were discussed. Deposition rate and crystallization of the films increased whereas the surface roughness decreased in the growth temperature range of 300–370 °C.

Key words: Aluminum nitride; plasma enhanced atomic layer deposition; growth rate; crystallization; surface roughness; deposition temperature

CLC number: O472⁺.1 **Document code:** A **DOI:** 10.3788/IRLA201645.0421001

PEALD 沉积温度对 AlN 的结构和表面特性的影响

陈 芳¹, 方 铨¹, 王双鹏², 牛守柱¹, 方芳³, 房 丹¹, 唐吉龙¹, 王晓华¹, 刘国军¹, 魏志鹏¹

(1. 长春理工大学 光电工程学院 高功率半导体激光国家重点实验室, 吉林 长春 130022;
2. 中国科学院长春光学精密机械与物理研究所 应用光学国家重点实验室, 吉林 长春 130022;
3. 南昌大学 国家硅基 LED 工程技术研究中心, 广西 南昌 330047)

摘 要: 研究通过等离子增强原子层沉积(PEALD)在不同沉积温度下生长的 AlN 温度对其特性的影响。前驱体是 NH_3 和 TMA, 在 300 °C、350 °C 和 370 °C 沉积温度下分别沉积了 200、500、800、1 000、1 500 周期的 AlN 层, 并讨论了 AlN 薄膜的生长速率、结晶化和表面粗糙度。结果表明, 在 300~370 °C 范围内, 随着温度的上升薄膜的沉积速率和结晶化增加, 而薄膜表面粗糙度减小。

关键词: 氮化铝; 等离子增强原子层沉积; 生长速率; 结晶化; 表面粗糙度; 沉积温度

收稿日期: 2015-08-21; 修订日期: 2015-09-17

基金项目: 国家自然科学基金(61076039, 61204065, 61205193, 61307045); 高等学校博士学科点专项科研基金(20112216120005); 吉林省科技发展规划(20121816, 201201116); 高功率半导体激光国家重点实验室基金(9140C310101120C031115)

作者简介: 陈芳(1989-), 女, 博士生, 主要从事光电子技术及应用方面的研究。Email: cf198909@163.com

通讯作者: 方铨(1983-), 男, 助理研究员, 主要从事半导体光电子学方面的研究。Email: fangxuan110@126.com

0 Introduction

Good thermal conductivity and high band gap makes Aluminum nitride (AlN) become an excellent material for several applications. AlN has been used in UV range light emitting diodes^[1], high- k stacks^[2], dye-sensitized solar cells^[3], and for gallium arsenide and silicon carbide passivation^[4-5]. AlN^[6-8] has been grown by metal organic vapor phase epitaxy(MOVPE), plasma enhanced chemical vapor deposition(PECVD) and molecular beam epitaxy (MBE). Due to the accurate thickness control, uniformity and especially high conformality^[9], plasma enhanced atomic layer deposition (PEALD) processes have also been developed for AlN using trimethylaluminum(TMA) as the aluminum source and ammonia(NH₃) as the source for nitrogen. However, in order to get a sufficient growth rate with NH₃, the growth temperature has to be above 400 °C^[10]. Therefore, for lower temperature deposition it is reasonable to use plasma to improve the reactivity of NH₃.

Although the growth process of PEALD AlN based on TMA and NH₃ plasma has been published by Liu et al.^[10], the properties of the PEALD grown AlN films at different temperature have not been extensively studied previously. In this paper the effect of the growth temperature on the growth rate, surface roughness and crystallization of the AlN films was investigated.

1 Experimental detail

PEALD processes have been developed for preparing AlN using trimethylaluminum (TMA) as the aluminum source and NH₃ plasma as the source for nitrogen, which were grown by a LabNano PE TM Plasma/Thermal ALD reactor equipped with a capacitive plasma source. TMA and NH₃ enhanced by argon (Ar₂) plasma were used as precursors while Ar₂ was used as the carrier gas. Ar₂ flow was controlled by mass flow controllers(MFCs). TMA was pulsed for

0.8 s and NH₃ for 10 s while the purge times after the TMA and NH₃ pulses were 3 and 1 s, respectively. Plasma power was set to 300 W and turned on before the NH₃ pulse and off before TMA pulse in each cycle. To investigate the influence of growth temperature on the AlN film properties, 200, 500, 800, 1 000, 1 500 cycles AlN layers were deposited at 300 °C, 350 °C and 370 °C.

In this paper, we study the properties of the AlN film deposited on Al₂O₃ surface at different temperatures. Atomic Force Microscope (AFM) is applied to characterize the topography and the roughness of the deposited films at different temperatures. X-ray Diffraction (XRD) was used to determine the crystallinity of the AlN films (Bruker AXS D8 DAVINCI) with Cu K α radiation of 0.154 06 nm.

2 Results and discussion

The film thickness as a function of the ALD cycles is shown in Fig.1. One can see that the film thickness has almost linear dependence on the ALD cycles but the growth temperature affects the growth rate. Deposition rate increased linearly from 0.74, 1.04, 1.32 Å/cycle in the growth temperature of 300 °C, 350 °C and 370 °C. The result in this paper is corresponded with the previous reference^[11].

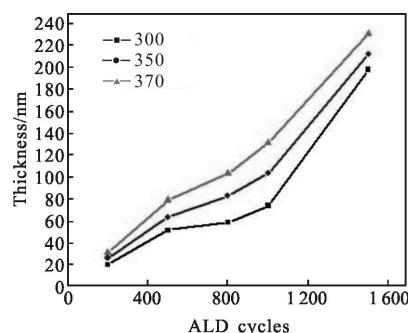


Fig.1 AlN film thickness as a function of the ALD cycles at different temperatures

X-ray diffraction curves from the AlN films grown at 300 °C, 350 °C and 370 °C are shown in Fig.2. It can be clearly seen that there formed AlN crystal

for AlN(102), AlN(110), AlN(103) and AlN(112)^[12-15] diffraction peaks are found, and diffraction peaks can be seen clearer with the temperature improvement, the crystallization of AlN films grown at 370 °C is the most significant.

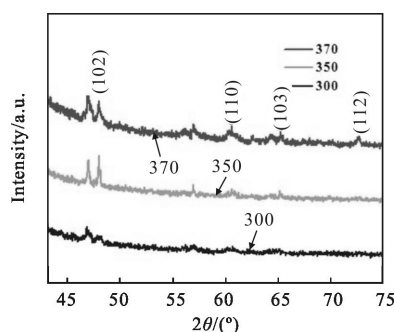


Fig.2 X-ray diffraction scans from 1 500 cycles AlN films grown at 300 °C, 350 °C and 370 °C

The surface morphology of PEALD AlN deposited on Al₂O₃ at different temperatures was also investigated by AFM. As shown in Fig.3, 1500 cycles AlN films grown at 300 °C(Fig.3 (a)), 350 °C(Fig.3 (b)) and 370 °C (Fig.3(c)). The AlN layers grown on sapphire substrates

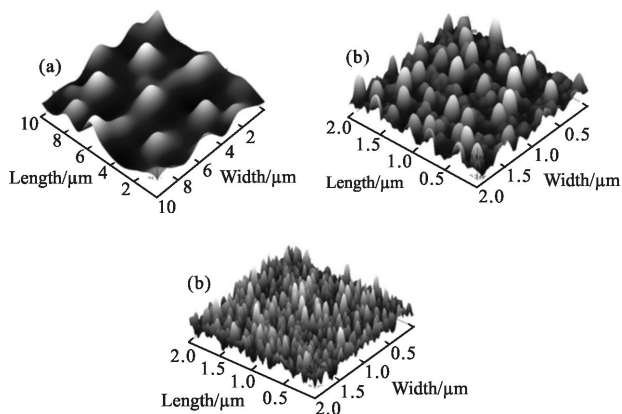


Fig.3 AFM images of 1500 cycles AlN films grown at 300 °C (a), 350 °C (b) and 370 °C (c), respectively

showed a very interesting feature. The growth is very similar to that observed ZnO layers grown on sapphire substrates^[16]. It is evident from all the images that the AlN exhibits an island-like growth on sapphire substrates. There are AlN islands scattered over the surface. It also can be seen that the AlN layers

deposited on different temperatures significantly affect the surface morphology of the samples. The roughness of the samples is 5.98 nm, 1.77 nm and 0.376 nm which deposited on 300 °C, 350 °C and 370 °C, respectively. Thus, we can know that the roughness decreased with the temperature improvement.

3 Conclusion

In summary, the structural and surface properties of AlN films grown in the temperature range of 300–370 °C by plasma enhanced ALD using TMA and NH₃ precursors. Deposition rate increased linearly from 0.74, 1.04, 1.32 Å/cycle in the growth temperature of 300 °C, 350 °C and 370 °C, respectively. The surface roughness decreased with the temperature improvement. The films grown at each temperature were found to be crystalline and the highest growth temperature the AlN film crystalline significantly.

References:

- [1] Taniyasu Y, Kasu M, Makimoto T. An aluminium nitride light-emitting diode with a wavelength of 210 nanometres [J]. *Nature*, 2006, 441: 325.
- [2] Chobpattana V, Mikhchev E, Zhang J Y, et al. Extremely scaled high-k/In_{0.53}Ga_{0.47}As gate stacks with low leakage and low interface trap densities [J]. *Journal of Applied Physics*, 2014, 116(12): 124104.
- [3] Reid K G, Dip A, Sasaki S, et al. Electrical and materials properties of AlN/HfO₂ high-k stack with a metal gate[J]. *Thin Solid Films*, 2009, 517: 2712–2718.
- [4] Huang K C, Chen P Y, Vittal R, et al. Enhanced performance of a quasi-solid-state dye-sensitized solar cell with aluminum nitride in its gel polymer electrolyte [J]. *Solar Energy Materials and Solar Cells*, 2011, 95 (8): 1990–1995.
- [5] Bosund M, Mattila P, Aierken A, et al. GaAs surface passivation by plasma-enhanced atomic layer deposited aluminum nitride [J]. *Applied Surface Science*, 2010, 256 (24): 7434–7437.
- [6] Liu H, Bertolet D C, Rogers J W. The surface chemistry of aluminum nitride MOCVD on alumina using trimethylaluminum and ammonia as precursors [J]. *Surface Science*, 1994, 320 (1–2): 145–160.

- [7] Zhang Kefeng, Li Tao, Tang Hengjing, et al. Effect of AlN passivation on mesa structured PIN InGaAs detector [J]. *Infrared and Laser Engineering*, 2009, 38(3): 402. (in Chinese)
- [8] Stevens K S, Ohtani A, Kinniburgh M, et al. Structural and mechanical characteristics of (103) AlN thin films prepared by radio frequency magnetron sputtering [J]. *Appl Phys Lett*, 2009, 65 (3):321–323.
- [9] Dendooven J, Deduytsche D, Musschoot J, et al. Conformality of Al₂O₃ and AlN deposited by plasma-enhanced atomic layer deposition [J]. *Journal of the Electrochemical Society*, 2010, 157(4): 111–116.
- [10] Liu X, Ramanathan S, Lee E, et al. Atomic layer deposition of aluminum nitride thin films from trimethyl aluminum (TMA) and ammonia [J]. *Mater Res Soc Symp Proc*, 2004, 811: 191–196.
- [11] Markus Bosund, Timo Sajavaara, Mikko Laitinen, et al. Properties of AlN grown by plasma enhanced atomic layer deposition [J]. *Applied Surface Science*, 2011, 257: 7827–7830.
- [12] Hairong Hu, Zhiguo Wu, Weibo Zhang, et al. Effect of Mg doping on growth and photoluminescence of AlN hexagonal nanorods [J]. *Journal of Alloys and Compounds*, 2015, 624: 241–246.
- [13] Xu Xiaohong, Wu Haishun, Zhang Congjie, et al. Morphological properties of AlN piezoelectric thin films deposited by DC reactive magnetron sputtering [J]. *Thin Solid Films*, 2001, 388: 62–67.
- [14] Cagla Ozgit, Inci Donmez, Mustafa Alevli, et al. Self-limiting low-temperature growth of crystalline AlN thin films by plasma-enhanced atomic layer deposition [J]. *Thin Solid Films*, 2012, 520: 2750–2755.
- [15] Engelmark F, Fucntes G, Katardjiev I V, et al. Synthesis of highly oriented piezoelectric AlN films by reactive sputter deposition[J]. *Journal of Vacuum Science & Technology A*, 2000, 18: 1609.
- [16] Zsofia Baji, Zoltan Labadi, Zsolt E Horvath, et al. Nucleation and growth modes of ALD ZnO [J]. *Cryst Growth Des*, 2012, 12(11): 5615–5620.