



High response and excellent selectivity acetone sensor based on γ -Fe₂O₃ hollow microspheres

Qixuan Qin^a, Xindong Zhang^{a,*}, Nan Zhang^{b,*}

^a State Key Laboratory of Integrated Optoelectronics, College of Electronic Science and Engineering, Jilin University, 2699 Qianjin Street, Changchun 130012, People's Republic of China

^b Changchun Institute of Optics, Fine Mechanics and Physics, CAS, Changchun 130033, People's Republic of China

ARTICLE INFO

Keywords:

γ -Fe₂O₃
Hollow microspheres
Acetone sensor
High response
Excellent selectivity

ABSTRACT

The γ -Fe₂O₃ hollow microspheres were synthesized by a simple solvothermal method and a subsequent two-step annealing process. The sensor based on γ -Fe₂O₃ hollow microspheres exhibited an ultra-fast response time (1s), high response (232.7), and excellent selectivity to 100 ppm acetone at the optimum operating temperature (173 °C). The excellent gas sensing performance could be attributed to the large specific surface area (182.6 m²g⁻¹) and a large number of oxygen vacancies, which would enhance the adsorption of oxygen molecules on the surface of the material. Moreover, the sensor achieves a response of 5.64 to 1 ppm acetone, which enables the prepared γ -Fe₂O₃ hollow microspheres a promising candidate for clinical detection of diabetic ketosis.

1. Introduction

Acetone is considered a marker for the clinical detection of diabetes mellitus. Non-invasive and painless detection of diabetes can be achieved by detecting acetone in the exhaled breath of diabetic patients. The threshold of acetone concentration in exhaled gas for clinical detection of diabetes is 1.8 ppm [1]. Therefore, the development of a miniaturized acetone gas sensor with low cost, high sensitivity, excellent selectivity, low detection limit, and fast response is of great significance for the clinical detection of diabetes mellitus. As a promising magnetic material, γ -Fe₂O₃ has been widely used as high-density magnetic material, catalyst, water treatment, and pigment. Meanwhile, owing to the advantages of low cost and high sensitivity, γ -Fe₂O₃ can be used as a sensing material to detect polluting gases and volatile organic compound gases (VOCs). For example, Zhang et al. prepared a high-sensitivity H₂S sensor based on γ -Fe₂O₃ ($R_{\text{air}}/R_{\text{gas}} = 520.73$, 97 ppm) [2]. Song et al. prepared hollowed-out hierarchical γ -Fe₂O₃ microrods to 100 ppm acetone with a response of 125.5 [3]. In this work, γ -Fe₂O₃ hollow microspheres were synthesized by the solvent thermal method, and their gas sensing properties were investigated.

2. Experimental

2.1. Synthesis of Fe₂O₃ hollow microspheres

Ferric nitrate monohydrate (Fe(NO₃)₃·9H₂O, 99.8 %), glycerinum (C₃H₈O₃), and ethanol absolute (C₂H₅OH) were purchased from Beijing Chemical Works. All chemicals were used without further treatment. In a typical synthesis, 0.271 g of Fe(NO₃)₃·9H₂O was dissolved in a mixed solution of 10 mL of glycerol and 70 mL of isopropanol, stirred magnetically for 10 min, and then poured the homogeneous clear solution into a 100 mL Teflon-lined stainless steel autoclave and reacted at 190 °C for 12 h. After the autoclave was cooled to room temperature, the product was centrifuged and washed several times with deionized water and ethanol, and then dried at 70 °C for 12 h. The product was then calcined in a tube furnace at 350 °C for 2 h in an N₂ and air atmosphere at a heating rate of 1 °C min⁻¹, respectively. A reddish-brown powder was obtained.

2.2. Characterization

The crystal structure and chemical states of the sample were investigated via X-ray powder diffraction (XRD) and X-ray photoelectron spectroscopy (XPS). The morphologies of the sample is observed by scanning electron microscopy (SEM). The specific surface area and pore

* Corresponding authors.

E-mail addresses: xindong@jlu.edu.cn (X. Zhang), zhangnan@ciomp.ac.cn (N. Zhang).

<https://doi.org/10.1016/j.matlet.2022.133337>

Received 23 September 2022; Received in revised form 8 October 2022; Accepted 10 October 2022

Available online 14 October 2022

0167-577X/© 2022 Elsevier B.V. All rights reserved.

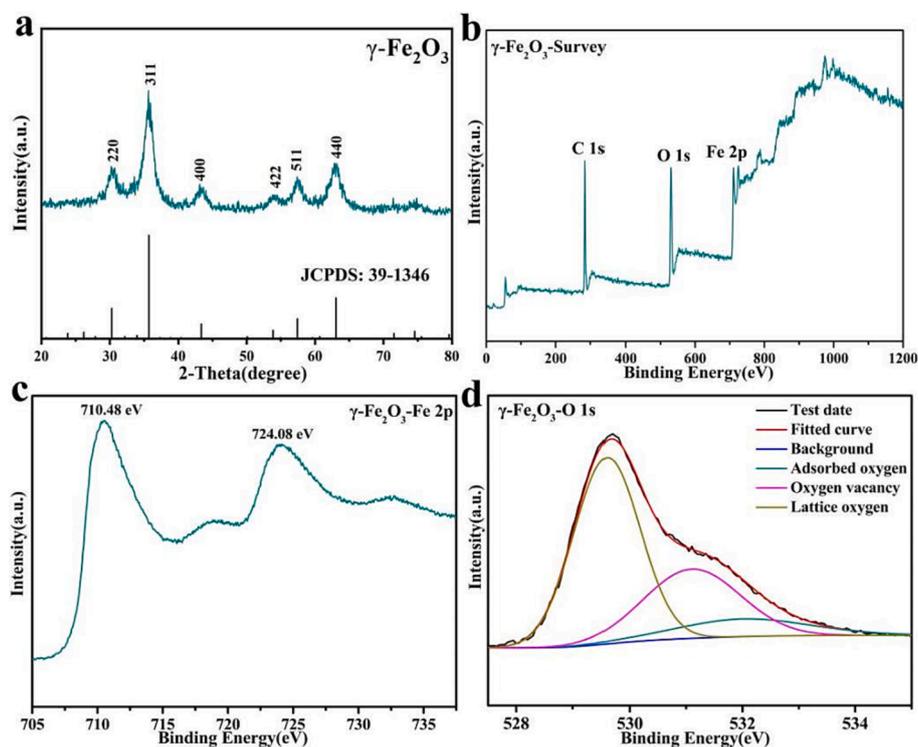


Fig. 1. (a) XRD pattern, (b) XPS survey spectra, (c) High resolution Fe 2p spectra, and (d) high resolution O 1s spectra of the γ -Fe₂O₃ hollow microspheres.

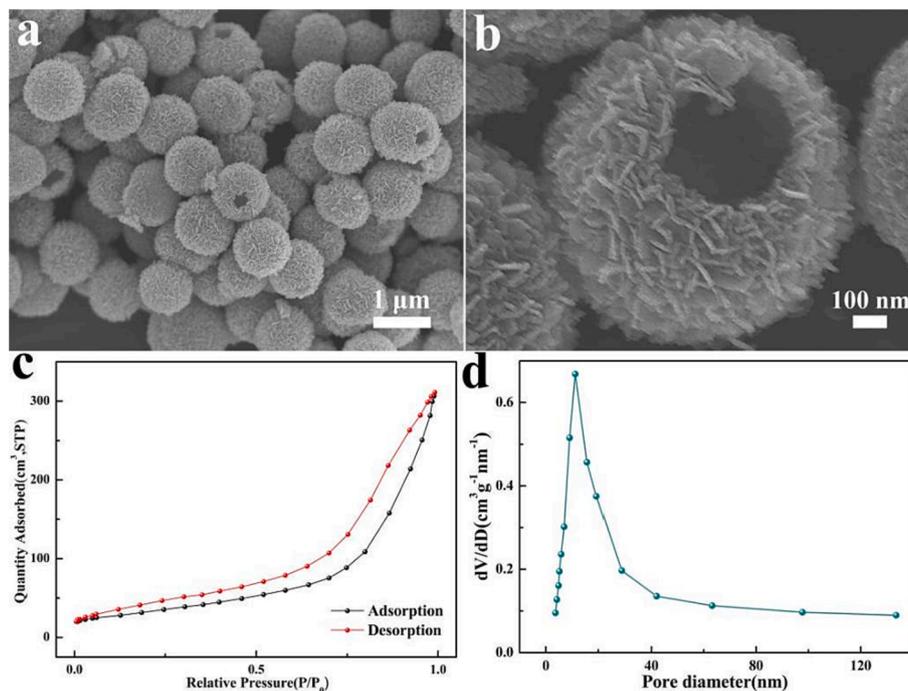


Fig. 2. FESEM images of γ -Fe₂O₃ hollow microspheres: (a) Low magnification; (b) high magnification. (c) Nitrogen adsorption–desorption isotherms and (d) Pore size distribution plot of γ -Fe₂O₃ hollow microspheres.

size distribution of the sample were analyzed by Brunauer Emmette Teller (BET) and Barrett-Joyner-Halenda (BJH), respectively. The performances of the gas sensor were carried out by a CGS-8 intelligent gas sensing analysis system. The response of the sensor was defined as $S = R_a/R_g$. R_a and R_g represent the resistance of the sensor in air and the target gas, respectively. The response and recovery time are defined as the time it takes for the sensor to complete 90 % of the total resistance

change during the response and recovery process.

3. Results and discussion

3.1. Characterization

It can be seen from XRD characterization (Fig. 1a) that all the

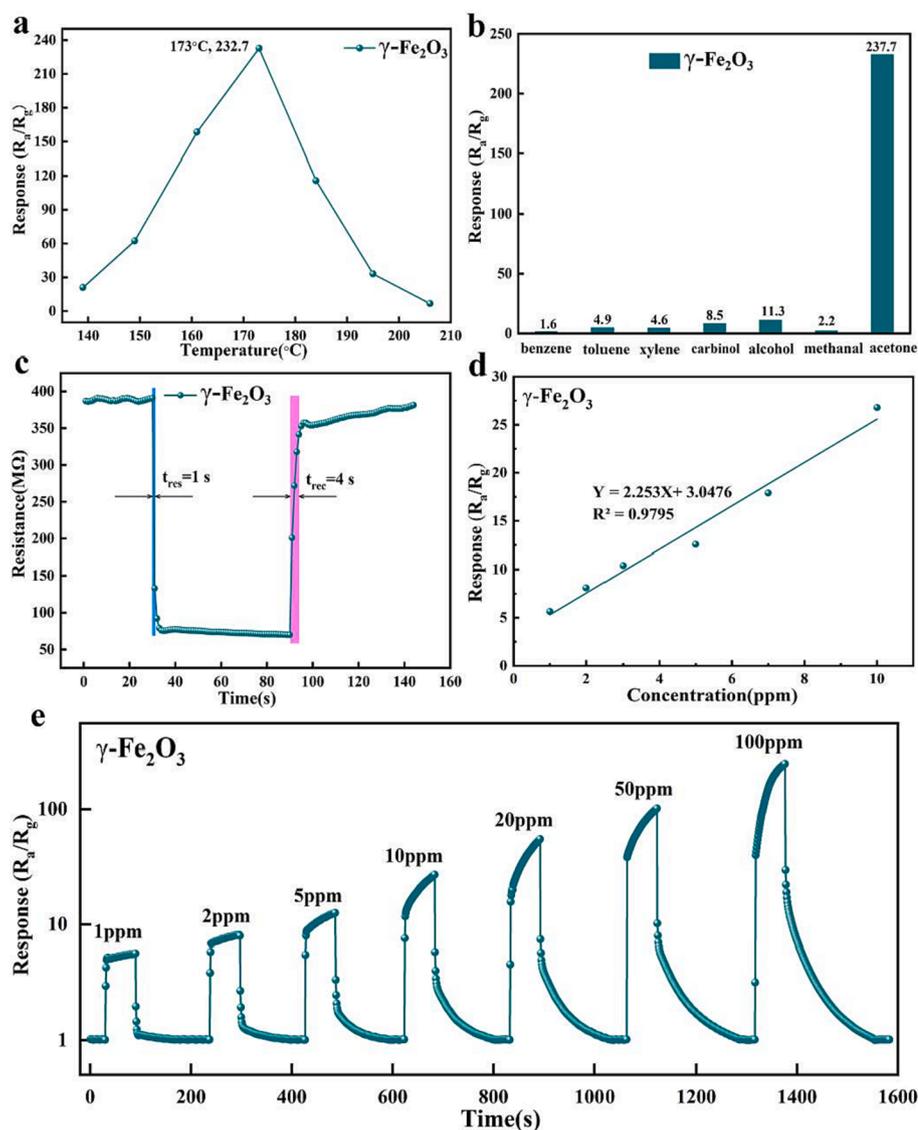


Fig. 3. (a) Responses of the γ -Fe₂O₃ sensor to 100 ppm acetone at different operating temperatures, (b) Responses of the γ -Fe₂O₃ sensor to 100 ppm various tested gases at 173 °C. (c) The resistance transient curve of the γ -Fe₂O₃ sensor to 100 ppm acetone at 173 °C. (d) Responses of the sensor based on γ -Fe₂O₃ hollow microspheres as a function of acetone concentration (1–10 ppm) at 173 °C. (e) Concentration-dependent response curves of the γ -Fe₂O₃ sensor to 1–100 ppm acetone at 173 °C.

apparent diffraction peaks correspond well to the standard card of γ -Fe₂O₃ (JCPDS Card No. 39-1346), indicating that the synthesized material is γ -Fe₂O₃ with high purity and good crystallinity [4]. The XPS spectrum indicates that only C, Fe and O were observed, where C was introduced as a reference standard (Fig. 1b). Fig. 1c shows that the two peaks in the Fe 2p spectrum located at 710.48 and 724.08 eV corresponding to Fe 2p_{3/2} and Fe 2p_{1/2} can be attributed to Fe³⁺. The XPS spectrum of O 1s shown in Fig. 1d can be further decomposed into three individual peaks with binding energies at 529.58, 531.08, and 532.18 eV, which can be attributed to lattice oxygen, oxygen vacancies, and chemisorbed oxygen, respectively. The percentage of oxygen vacancies is 31.2 %, which facilitates the adsorption of oxygen molecules on the surface of the material and therefore improves its gas sensing performance [5]. The SEM images (Fig. 2a and b) show that the morphologies of the prepared γ -Fe₂O₃ sample are uniform hollow microspheres with a diameter of about 0.8–1 μ m. The BJH characterization result indicates that the prepared γ -Fe₂O₃ hollow nanospheres have a mesoporous structure (Fig. 2c) with a pore size of about 11.2 nm. The BET characterization result shows that the γ -Fe₂O₃ hollow nanospheres have a large specific surface area (182.6 m²g⁻¹), which can facilitate the adsorption of gas molecules on the surface of the material (Fig. 2d).

3.2. Gas sensing characteristics

To determine the optimum operating temperature of the γ -Fe₂O₃ sensor, the responses to 100 ppm acetone gas were tested in the range of 140–210 °C and the results were shown in Fig. 3a. The response of the γ -Fe₂O₃ sensor reaches its maximum value (232.7) when the operating temperature is 173 °C. Therefore, 173 °C is considered to be the optimum operating temperature for the γ -Fe₂O₃ sensor. This “increase-maximum-decrease” phenomenon can be explained by the following processes. As the operating temperature increases, the acetone molecules gain enough energy to overcome the activation energy barrier and react with the adsorbed oxygen. However, when the temperature is too high, the adsorption capacity of the gas decreases, resulting in a decrease in the response. All subsequent gas sensing performance tests are carried out at 173 °C. Fig. 3b shows the cross-response properties of the γ -Fe₂O₃ sensor for several VOC gases with a concentration of 100 ppm. It is clear that the prepared γ -Fe₂O₃ hollow nanospheres show the highest response to acetone. Fig. 3c shows the resistance transient curve of the γ -Fe₂O₃ sensor to 100 ppm acetone at 173 °C. It can be seen that the response and recovery time are 1 and 4s, indicating that the γ -Fe₂O₃ sensor can achieve rapid detection of acetone.

When the sensor was exposed to lower concentrations of acetone (1–10 ppm), the relationships between the concentrations of acetone

Table 1

The acetone sensing performances of gas sensors based on similar materials reported in the literature.

Sensing Materials	Conc/ ppm	Response	Res/rec time (s)	Temp/ °C	Ref.
γ -Fe ₂ O ₃ microrods	100	125.5	0.9/15	220	[3]
α/γ -Fe ₂ O ₃ micro flowers	1500	160	95/25	320	[6]
alpha-Fe ₂ O ₃ hollow spheres	100	46.6	1/12	220.4	[7]
3D α -Fe ₂ O ₃	50	19.14	7/8	220	[8]
γ -Fe ₂ O ₃ hollow microspheres	100	232.7	1/4	173	This work

Conc.: Concentration; Res: Response; Temp: Temperature; Ref: Reference.

and the corresponding responses are shown in Fig. 3d. The concentration–response curve can be fitted as $Y = 2.253X + 3.0476$, where Y is the response of the sensor and X is the concentration of the tested acetone gas. The correlation coefficient R^2 was 0.9795, indicating a good linear relationship. The response of the sensor to 1 ppm acetone is 5.64, but the clinical threshold for diagnosing diabetes is 1.8 ppm, thus satisfying the need for clinical diagnosis of diabetes. The acetone concentration-dependent response curve of the γ -Fe₂O₃ sensor exhibits good reproducibility and reversibility (Fig. 3e). To evaluate the sensing performances of γ -Fe₂O₃ hollow microspheres, we listed the acetone sensing performances of γ -Fe₂O₃ hollow microspheres and several similar materials (Table 1), indicating that our sensor has the best sensing performances to acetone [6–8].

3.3. Gas sensing mechanism

γ -Fe₂O₃ is a typical *n*-type semiconductor where the main carriers are free electrons. When the γ -Fe₂O₃ sensor is exposed to air, O₂ molecules adsorbed on the surface of the material captures the free electrons from the conduction band to convert into adsorbed oxygen negative ions (O₂⁻ and O⁻), thus reducing the concentration of conducting electrons and exhibiting a high resistance state [7]. When the γ -Fe₂O₃ sensor is exposed to an acetone atmosphere, the adsorbed acetone gas molecules react with the adsorbed oxygen ions to produce carbon dioxide and water vapor [9,10]. During this process, free electrons trapped by oxygen molecules are released into the conduction band, which will result in a narrowing of the electron depletion layer and therefore a decrease in the resistance of the sensor.

4. Conclusions

In this work, γ -Fe₂O₃ hollow microspheres were prepared by a combination of a solvothermal method and a two-step calcination treatment. The prepared γ -Fe₂O₃ sensor shows a fast response/recovery time (1/4 s) and achieves a high response of 232.7 to 100 ppm acetone. It also has an ideal response (5.64) to low concentration (1 ppm) of acetone, which is completely adequate for the clinical diagnosis of diabetes.

CRedit authorship contribution statement

Qixuan Qin: Investigation, Conceptualization, Methodology, Writing – original draft. **Xindong Zhang:** Supervision, Data curation, Writing – review & editing. **Nan Zhang:** Funding acquisition, Writing – review & editing.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Data availability

No data was used for the research described in the article.

Acknowledgment

The authors acknowledge support from the Natural Science Foundation of Jilin Province (Grants 20220508030RC).

References

- [1] S. Lv, J. Fan, F. Liu, Y. Zhang, L. Jiang, S. Ouyang, C. Zhang, C.G. Wang, P. Sun, L. J. Wang, G.Y. Lu, YSZ-based mixed potential type acetone gas sensor attached with CuSb₂O₆ sensing electrode for ketosis diagnosis, *Sens. Actuators B Chem.* 370 (2022), 132408.
- [2] C.X. Zhang, S. Zhang, Y. Yang, H. Yu, X.T. Dong, Highly sensitive H₂S sensors based on metal-organic framework driven gamma-Fe₂O₃ on reduced graphene oxide composites at room temperature, *Sens. Actuators B Chem.* 325 (2020), 128804.
- [3] Z.J. Song, H.M. Chen, S.S. Bao, Z.X. Xie, Q. Kuang, L.S. Zheng, Nanosheet-assembled, hollowed-out hierarchical gamma-Fe₂O₃ microrods for high-performance gas sensing, *J. Mater. Chem. A* 8 (2020) 3754–3762.
- [4] H.V. Hai, N.D. Cuong, H.D. Mai, H.T. Long, T.Q. Phuong, T.K. Dang, L.V. Thong, N. N. Viet, N. Van Hieu, Superior detection and classification of ethanol and acetone using 3D ultra-porous gamma-Fe₂O₃ nanocubes-based sensor, *Sens. Actuators B Chem.* 362 (2022), 131737.
- [5] T. Yang, L. Du, C. Zhai, Z. Li, Q. Zhao, Y. Luo, D.J. Xing, M.Z. Zhang, Ultrafast response and recovery trimethylamine sensor based on alpha-Fe₂O₃ snowflake-like hierarchical architectures, *J. Alloys Compd.* 718 (2017) 396–404.
- [6] V.X. Hien, L.H. Phuoc, C.T. Khoa, D.D. Vuong, N.D. Chien, High acetone-sensing performance of bi-phase alpha-/gamma-Fe₂O₃ submicron flowers grown using an iron plate, *J. Sci. Adv. Mater. Dev.* 6 (2021) 27–32.
- [7] Q. Qin, X. Zhu, X. Zhang, Synthesis of alpha-Fe₂O₃ hollow spheres with rapid response and excellent selectivity towards acetone, *Mater. Sci. Eng. B Adv. Funct. Solid State Mater.* 275 (2022), 115482.
- [8] H.J. Song, S.W. Yan, Y.L. Yao, L.X. Xia, X.H. Jia, J.S. Xu, 3D alpha-Fe₂O₃ nanorod arrays/graphene oxide nanosheets as sensing materials for improved gas sensitivity, *Chem. Eng. J.* 370 (2019) 1331–1340.
- [9] S.J. Young, Y.H. Liu, Z.D. Lin, K. Ahmed, M.N.I. Shiblee, S. Romanuik, P.K. Sekhar, T. Thundat, L. Nagahara, S. Arya, R. Ahmed, H. Furukawa, A. Khosla, Multi-walled carbon nanotubes decorated with silver nanoparticles for acetone gas sensing at room temperature, *J. Electrochem. Soc.* 167 (2020), 167519.
- [10] Y.Z. Fan, W. Wang, J.F. Zhang, Y. Lu, C.X. Liu, S. Adimi, J.R. Zhou, S.P. Ruan, Y. Chen, Construction of p-n heterojunctions by modifying MOF-derived alpha-Fe₂O₃ with partially covered cobalt tungstate for high-performance ethyl acetate detection, *Sens. Actuators B Chem.* 344 (2021), 130129.